

## Chapter 32

# Magneto-Optical and Magnetic Properties of Three-Layer Films Based on Permalloy and Copper



V. B. Loboda, Yu. O. Shkurdoda, Yu. M. Shabelnyk, A. M. Chornous, S. M. Khursenko, L. V. Dekhtyaruk, K. Merkotan and O. O. Drozdenko

**Abstract** Three-layer nanostructured films  $\text{Fe}_x\text{Ni}_{100-x}/\text{Cu}/\text{Fe}_x\text{Ni}_{100-x}$  ( $x \cong 50$ ,  $d_{\text{FeNi}} = 40$  nm;  $d_{\text{Cu}} = 5$  nm) consisting of  $\text{Fe}_{0.5}\text{Ni}_{0.5}$  alloy layers separated by Cu layer were obtained by layers-by-layers vacuum condensation at the pressure of  $10^{-4}$  Pa. Magnetic hysteresis loops of three-layer films were obtained using a vibration magnetometer. Magnetic hysteresis loops obtained in transverse geometry have an almost rectangular shape with sharp magnetization reversal. The magnetization reversal of the films completely changes in the magnetic field range with induction of  $-25$  to  $25$  mT for freshly condensed films and  $-30$  to  $30$  mT for thermostabilized films. The rectangular hysteresis contour is typical for single-layer films of ferromagnetic metals and alloys based on them and indicates the presence of an axis of easy magnetization in the sample plane. Magnetization in the direction perpendicular to the film plane shows the effect of a strong demagnetizing field. After thermal stabilization of the films, the dependence does not change significantly, except for an increase in the residual magnetization and coercive force (more pronounced hysteresis).

---

V. B. Loboda · S. M. Khursenko

Sumy National Agrarian University, 160, Herasym Kondratiev Str, Sumy 40021, Ukraine

Yu. O. Shkurdoda (✉) · Yu. M. Shabelnyk · A. M. Chornous · O. O. Drozdenko

Sumy State University, Rimsky-Korsakov Str., 2, Sumy 40007, Ukraine

e-mail: yu.shkurdoda@gmail.com

L. V. Dekhtyaruk

Kharkiv National University of Construction and Architecture, 40, Sumska Str, Kharkiv 61002, Ukraine

K. Merkotan

Odesa National Polytechnic University, 1, Shevchenko Ave, Odesa 65044, Ukraine

© Springer Nature Singapore Pte Ltd. 2020

A. D. Pogrebnjak and O. Bondar (eds.), *Microstructure and Properties of Micro- and Nanoscale Materials, Films, and Coatings (NAP 2019)*,

Springer Proceedings in Physics 240, [https://doi.org/10.1007/978-981-15-1742-6\\_32](https://doi.org/10.1007/978-981-15-1742-6_32)

## 32.1 Introduction

Currently, an intensive study of the physical properties of new film materials is being carried out in connection with their wide practical use as functional elements of instrument structures [1–8] and protective coatings [9–18]. The study of magnetically inhomogeneous film materials (multilayer structures, granular films, composites, etc.) made it possible at the end of the twentieth century to discover a number of important magnetoresistive effects—giant magnetoresistance (GMS), tunneling magnetoresistance (TMS), colossal magnetoresistance, etc. [19–23].

Multilayer film systems based on permalloy (Py) and copper, in which spin-dependent electron scattering is realized, are widely used as effective magnetic field sensors, digital magnetoresistive memory devices, automotive electronics, biomedical technologies, etc. But despite this, there is a need for further search and experimental study of film structures that would satisfy additional requirements (minimum dimensions, high sensitivity, high reproduction samples, etc.). Also important is the task of predicting the behavior of the electrical and magnetoresistive properties of multilayer systems with a change in the thickness of the metal layers, structure, temperature, and external magnetic field. The solution to such problems is possible only under the condition of using an integrated approach to the study of the physical properties of film systems.

The purpose of this work is a comprehensive study of the magnetic structure and magnetic parameters of magnetic three-layer films based on permalloy and copper.

---


## 32.2 Experiment Details

Investigated samples with a thickness of 5–100 nm were obtained by evaporation and condensation in the vacuum chamber of VUP-5 M (at the pressure of  $10^{-4}$  Pa). The films were condensed onto a glass substrate with pre-applied copper contacts with a substrate of chromium at room temperature. The rate of precipitation of the alloy was  $\omega = 0.5\text{--}1$  nm/s. Three-layer films consisting of  $\text{Fe}_{0.5}\text{Ni}_{0.5}$  alloy layers separated by Cu layer were obtained by layers-by-layers condensation. The construction of the lining holder allowed to receive two film samples in one cycle with a different thickness of the copper layer and with similar thicknesses of the alloy layers. For measuring their electrical resistance, the geometric dimensions of the films were set by windows in the nichrome foil mechanical masks, which made with high accuracy.

The percentage composition of the film was determined by x-ray microanalysis with an energy dispersive spectrometer (EDS).

### 32.3 Results and Discussion

To establish the relationship between the magnetoresistance of three-layer films with a change in their magnetic structure, a study was made of the domain structure of the films  $\text{Fe}_{0.5}\text{Ni}_{0.5}/\text{Cu}/\text{Fe}_{0.5}\text{Ni}_{0.5}/\text{S}$  with simultaneous measurement of the magnetoresistance of the films. To observe the domain structure of the films, the magneto-optical Kerr effect was used, which consists of rotating the plane of polarized light reflected from the surface of a magnetized ferromagnet by a certain angle  $\varphi$  of the plane of polarization. Due to the differences in the angles of rotation of the plane of polarization of light by neighboring domains (depending on the orientation of their magnetic fields), after passing the reflected light through the analyzer, a light contrast is observed between areas with different magnetization. This light contrast is insignificant, since the light reflected from the film surface is not plane-polarized, but polarized elliptically. In Fig. 32.1 shows the loop of magnetoresistive hysteresis and its connection with the domain structure of the upper layer of a freshly condensed three-layer  $\text{Fe}_x\text{Ni}_{100-x}/\text{Cu}/\text{Fe}_x\text{Ni}_{100-x}/\text{S}$  ( $x \cong 50$ ,  $d_F = 40$  nm;  $d_N = 5$  nm) with giant magnetoresistance. The magnitude of the isotropic magnetoresistance for freshly condensed films is 0.5–1%, depending on the thickness of the layers. Small values of isotropic magnetoresistance are caused by small sizes of crystallites, high defectiveness of layers, and shunting of the effect with a relatively thick nonmagnetic interlayer [24, 25].

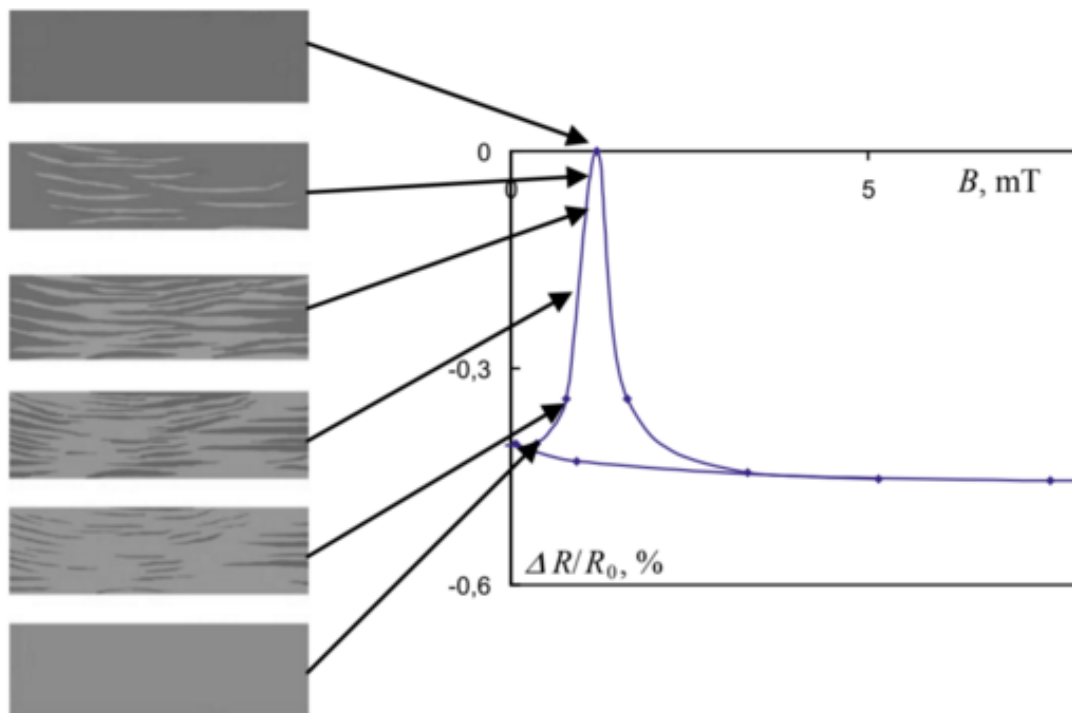

**Fig. 32.1** Domain structure and magnetic resistance loop of a freshly condensed three-layer film  $\text{Fe}_{0.5}\text{Ni}_{0.5}/\text{Cu}/\text{Fe}_{0.5}\text{Ni}_{0.5}/\text{S}$  ( $d_{\text{Py}} = 40$  nm;  $d_{\text{Cu}} = 5$  nm)